

Annual Technical Report

Large Area Lateral Epitaxial Overgrowth (LEO) of Gallium Nitride (GaN) Thin Films on Silicon Substrates and Their Characterization

Supported under Grant #N00014-98-1-0384
Office of the Chief of Naval Research
Report for the period 3/1/98-2/28/99

R. F. Davis, E. P. Carlson, T. Gehrke, K. Linthicum, T. P. Smith,
D. B. Thomson, and K. M. Tracy
Materials Science and Engineering Department
North Carolina State University
Campus Box 7907
Raleigh, NC 27695-7907

19990726 037

March, 1999

DISTRIBUTION STATEMENT A
Approved for Public Release
Distribution Unlimited

REPORT DOCUMENTATION PAGE

Form Approved
OMB No. 0704-0188

Public reporting burden for this collection of information is estimated to average 1 hour per response, including the time for reviewing instructions, searching existing data sources, gathering and maintaining the data needed, and completing and reviewing the collection of information. Send comments regarding this burden estimate or any other aspect of this collection of information, including suggestions for reducing this burden to Washington Headquarters Services, Directorate for Information Operations and Reports, 1215 Jefferson Davis Highway, Suite 1204, Arlington, VA 22202-4302, and to the Office of Management and Budget Paperwork Reduction Project (0704-0188), Washington, DC 20503.

1. AGENCY USE ONLY (Leave blank)		2. REPORT DATE March, 1999	3. REPORT TYPE AND DATES COVERED Annual: 3/1/98—2/28/99	
4. TITLE AND SUBTITLE Large Area Lateral Epitaxial Overgrowth (LEO) of Gallium Nitride (GaN) Thin Films on Silicon Substrates and Their Characterization			5. FUNDING NUMBERS 98PR04474-00 312 N68892 N66020 OECY3	
6. AUTHOR(S) R. F. Davis				
7. PERFORMING ORGANIZATION NAME(S) AND ADDRESS(ES) North Carolina State University Hillsborough Street Raleigh, NC 27695			8. PERFORMING ORGANIZATION REPORT NUMBER N00014-98-1-0384	
9. SPONSORING/MONITORING AGENCY NAMES(S) AND ADDRESS(ES) Sponsoring: ONR, Code 312, 800 N. Quincy, Arlington, VA 22217-5660 Monitoring: Administrative Grants Officer, Regional Office Atlanta Atlanta Regional Office 100 Alabama Street NW, Suite 4R15 Atlanta, GA 30303-3104			10. SPONSORING/MONITORING AGENCY REPORT NUMBER	
11. SUPPLEMENTARY NOTES				
12a. DISTRIBUTION/AVAILABILITY STATEMENT Approved for Public Release; Distribution Unlimited			12b. DISTRIBUTION CODE	
13. ABSTRACT (Maximum 200 words) Gallium nitride films have been grown on 6H-SiC substrates employing a new form of selective lateral epitaxy, namely pendeo-epitaxy. This technique forces regrowth to start exclusively on sidewalls of GaN seed structures. Both discrete pendeo-epitaxial microstructures and coalesced single crystal layers of GaN have been achieved. Analysis by SEM and TEM are used to evaluate the morphology of the resulting GaN films. Process routes leading to GaN pendeo-epitaxial growth using silicon substrates have also been achieved and the preliminary results are discussed.				
14. SUBJECT TERMS pendeo-epitaxy, gallium nitride, 6H-SiC, selective lateral epitaxy, pendeo-epitaxial growth, morphology			15. NUMBER OF PAGES 11	
			16. PRICE CODE	
17. SECURITY CLASSIFICATION OF REPORT UNCLAS	18. SECURITY CLASSIFICATION OF THIS PAGE UNCLAS	19. SECURITY CLASSIFICATION OF ABSTRACT UNCLAS	20. LIMITATION OF ABSTRACT SAR	

Process Routes for Low Defect-density GaN on Various Substrates Employing Pendeo-epitaxial Growth Techniques

K.J. Linthicum^{*}, T. Gehrke^{*}, D.B. Thomson^{*}, K.M. Tracy^{*}, E.P. Carlson^{*}, T. P. Smith^{*}, T.S. Zheleva^{**}, C.A. Zorman[†], M. Mehregany[†], and R.F. Davis^{*}

^{*}Department of Materials Science and Engineering, North Carolina State University, Raleigh, NC 27965

^{**}U.S. Army Research Laboratory, AMSRL-SE-EM, Adelphi, MD 20783

[†]Department of Electrical, Systems and Computer Engineering and Science, Case Western Reserve University, Cleveland, OH 44106

Abstract

GaN films have been grown on 6H-SiC substrates employing a new form of selective lateral epitaxy, namely pendeo-epitaxy. This technique forces regrowth to start exclusively on sidewalls of GaN seed structures. Both discrete pendeo-epitaxial microstructures and coalesced single crystal layers of GaN have been achieved. SEM and TEM analysis are used to evaluate the morphology of the resulting GaN films. Process routes leading to GaN pendeo-epitaxial growth using silicon substrates have also been achieved and the preliminary results are discussed.

A. Introduction

The III-nitride scientific community has been forced to grow thin films of GaN and related nitride materials using heteroepitaxial growth routes and techniques because of the dearth of bulk substrates of these materials. The resultant 10^8 – 10^{10} cm⁻² density of threading dislocations limits the properties of the resulting films and the devices fabricated in these materials. As such, there has been substantial research regarding selective area growth (SAG) and lateral epitaxial overgrowth (LEO) techniques for GaN deposition [1-9], fueled in part by the recent announcement by Nakamura, *et al.* [10] of the dramatic increase in projected lifetime of their GaN-based blue light-emitting laser diodes fabricated on LEO material. Using these approaches, researchers have been able to grow GaN films containing dislocation densities of $\approx 10^5$ cm⁻² in the areas of overgrowth. However, to benefit from this reduction in defects, the placement of devices incorporating LEO technology is limited and confined to regions on the final GaN device layer that are located on the overgrown regions.

In this paper, we report the achievement of a new approach to selective epitaxy of GaN, namely, pendeo- (from the Latin: to *hang* or be *suspended*) epitaxy (PE) as a promising new process route leading to a continuous, large area layer or discrete platforms of this material. An initial form of GaN pendeo-epitaxy without the use of a seed-mask was first reported by Zheleva *et al.*[11]. The current approach incorporates mechanisms of growth exploited by the conventional LEO process by using an amorphous mask to prevent vertical propagation of threading dislocations; however, it extends beyond the conventional LEO approach to employ the substrate itself as a *pseudo-mask* as discussed by Linthicum *et al.*[12]. This unconventional approach differs from LEO in that growth does not initiate through open windows on the (0001) surface of the GaN seed layer, instead it is forced to selectively begin on the side walls of a tailored microstructure comprised of forms previously etched into the seed layer. Continuation of the pendeo-epitaxial growth until coalescence over and between these forms results in a complete layer of low defect-density GaN. This is accomplished in one regrowth step, and the need to align devices or masks for the growth of a second layer over particular areas of overgrowth on the final GaN layer is eliminated. This approach may be more widely applicable than just GaN, as indicated by Gehrke *et al.*[15]. Additionally, we

report for the first time the ability to grow GaN pendeo-epitaxial films on silicon substrates. The achievement of GaN layers with surface areas limited only by the size of the available silicon substrates is now conceivable.

The following sections describe the experimental parameters necessary to achieve GaN films via PE, describe and discuss the microstructural evidence obtained for the resulting films and provide a summary of this research.

B. Experimental Procedures

Each pendeo-epitaxial GaN film and the underlying GaN seed layer and the AlN buffer layer were grown in a cold-wall, vertical pancake style RF inductively heated metallorganic vapor phase epitaxy (MOVPE) system. Two distinct process routes were explored for growth on (i) on-axis (0001)6H-SiC substrates and (ii) on-axis (111)Si substrates. In the former, each seed layer consisted of a 1 μm thick GaN film grown on a 100 nm thick AlN buffer layer previously deposited on a (0001) 6H-SiC substrate. Details of the experimental parameters used for the growth of these two layers are given in Ref. 13. In the growth on the Si substrates, a 1 μm (111)3C-SiC film was initially grown on a very thin (111)3C-SiC layer produced by conversion of the (111)Si surface via reaction with C_3H_8 entrained in H_2 . Both the conversion step and SiC film deposition were achieved using a cold-wall, vertical geometry, RF inductively heated atmospheric pressure chemical vapor deposition (APCVD) reactor. Details of the experimental parameters used for the conversion step and the growth of the 3C-SiC layer are given in Ref. 14. A 100 nm thick AlN buffer layer and a 1 μm GaN seed layer were subsequently deposited in the manner used for the 6H-SiC substrates and noted above.

A 100 nm silicon nitride growth mask was deposited on the seed layers via plasma enhanced CVD. A 150 nm nickel etch mask was subsequently deposited using e-beam evaporation. Patterning of the nickel mask layer was achieved using standard photolithography techniques followed by dipping in HNO_3 for approximately five minutes. The samples were subsequently cleaned by consecutive dips in trichloroethylene, acetone, methanol, and HCl for five minutes each and blown dry with nitrogen. The final, tailored,

microstructure consisting of seed forms was fabricated via removal of portions of the nickel etch mask via sputtering and by inductively coupled plasma (ICP) etching of portions of the silicon nitride growth mask, the GaN seed layer and the AlN buffer layer. Critical to the success of the pendeo-epitaxial growth, the etching of the seed-forms was continued completely through the exposed GaN and AlN layers and into either the 6H-SiC substrate or the 3C-SiC layer, thereby removing all III- nitride material from the areas between the side walls of the forms. The seed-forms used in this study were raised rectangular stripes oriented along the $\langle 1-100 \rangle$ direction, thereby providing a plurality of GaN sidewalls (nominally (11-20) faces). Seed form widths of 2 and 3 μm s coupled with separation distances of 3 and 7 μm s, respectively, were employed. The remaining nickel mask protecting the seed structures during the ICP etching process was removed using HNO_3 . Immediately prior to pendeo-epitaxial growth, the patterned samples were dipped in a 50% HCl solution to remove the surface oxide from the walls of the underlying GaN seed structures.

A schematic of the pendeo-epitaxial growth of GaN is illustrated in Fig. 1. There are three primary stages associated with the pendeo-epitaxial formation of this material: (i) initiation of lateral homoepitaxy from the sidewalls of the GaN seed, (ii) vertical growth and (iii) lateral growth over the silicon nitride mask covering the seed structure. Pendeo-epitaxial growth of GaN was achieved within the temperature range of 1050-1100°C and a total pressure of 45 Torr. The precursors (flow rates) of triethylgallium (26.1 $\mu\text{mol}/\text{min}$) and NH_3 (1500 sccm) were used in combination with a H_2 diluent (3000 sccm). Additional experimental details

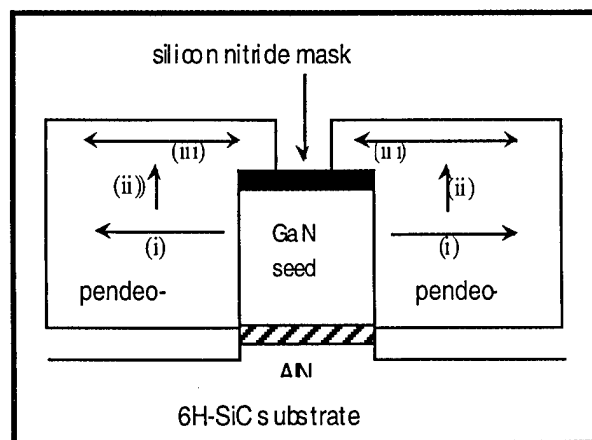


Figure 1. Schematic of GaN pendeo-epitaxial growth process steps.

regarding the pendeo-epitaxial growth of GaN and $\text{Al}_x\text{Ga}_{1-x}\text{N}$ layers employing 6H-SiC substrates are given in Refs. 15, 16, and 17. The morphology and defect microstructures were investigated using scanning electron microscopy (SEM) (JEOL 6400 FE) and transmission electron microscopy (TEM) (TOPCON 0002B, 200 KV).

C. Results and Discussion

The pendeo-epitaxial phenomenon is made possible by taking advantage of growth mechanisms identified by Zheleva *et al.*[7] in the conventional LEO technique, and by using two additional key steps, namely, the initiation of growth from a GaN face other than the (0001) and the use of the substrate (in this case SiC) as a mask. By capping the seed-forms with a growth mask, the GaN was forced to grow initially and selectively only on the GaN sidewalls. Common to conventional LEO, no growth occurred on the silicon nitride mask covering the seed forms. Deposition also did not occur on the exposed SiC surface areas at the higher growth temperatures employed to enhance lateral growth. The Ga- and N-containing species more likely either diffused along the surface or evaporated (rather than having sufficient time to form GaN nuclei) from both the silicon nitride mask and the silicon carbide substrate. The pronounced effect of this is shown in Fig. 2 wherein the newly deposited GaN has grown truly suspended (*pendeo*-) from the sidewalls of the GaN seed structure. During the second PE event (ii), vertical growth of GaN occurred from the advancing (0001) face of the laterally growing GaN. Once the vertical growth became extended to a height greater than

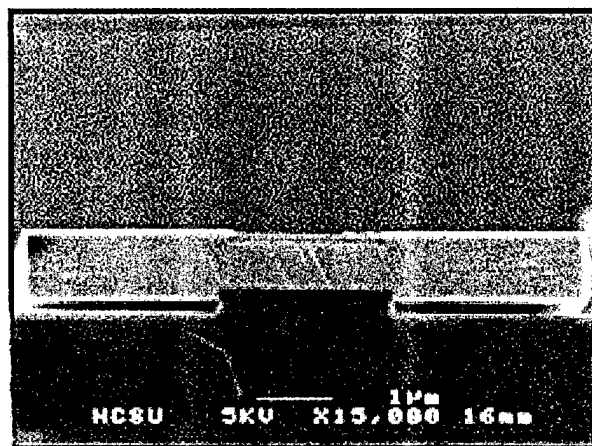


Figure 2. Cross-sectional SEM of a GaN pendeo-epitaxial growth structure with limited vertical growth from the seed sidewalls and no growth on the seed mask.

the silicon nitride mask, the third PE event (iii) occurred, namely, conventional LEO-type growth and eventual coalescence over the seed structure, as shown in Fig. 3. A cross-sectional TEM micrograph showing a typical pendeo-epitaxial growth structure is shown in Fig. 4. Threading dislocations extending into the GaN seed structure, originating from the GaN/AlN and AlN/SiC interfaces, are clearly visible.

The silicon nitride mask acted as a barrier to the further vertical propagation of these defects into the laterally overgrown pendeo-epitaxial film. Since the newly deposited GaN is suspended above the SiC substrate, there are no defects associated with the mismatches in

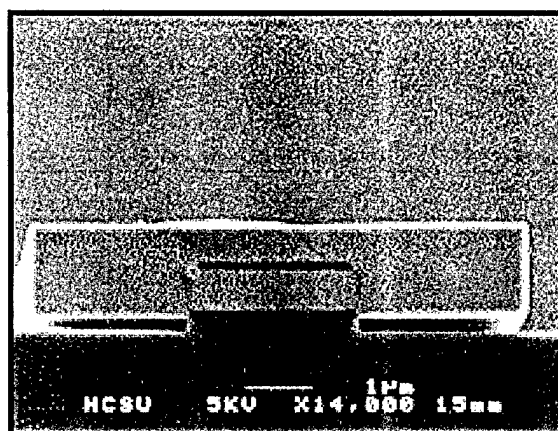


Figure 3. Cross-sectional SEM of a GaN/AlGaN pendeo-epitaxial growth structure showing coalescence over the seed mask.

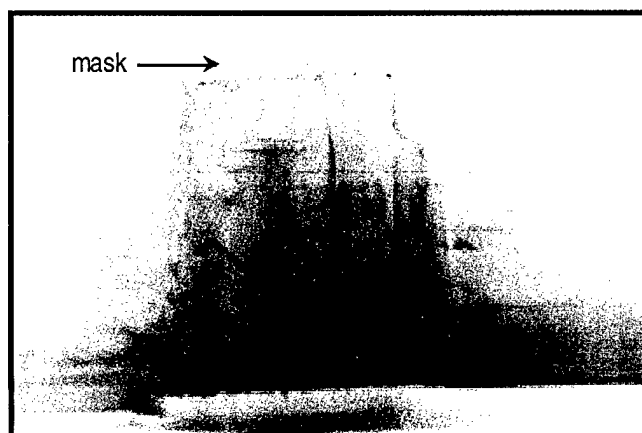


Figure 4. Cross-sectional TEM of a GaN pendeo-epitaxial growth structure showing confinement of threading dislocation under the seed mask, and a drastic reduction of defects in the regrown areas.

lattice parameters between GaN and AlN and between AlN and SiC. Preliminary analysis of the GaN seed/GaN pendeo-epitaxy interface revealed evidence of threading dislocations or stacking faults within the (0001) planes. This indicates evidence of the lateral propagation of the defects, however, there is yet no evidence that the defects reach the (0001) surface where device layers will be grown. As in the case LEO, there is a significant reduction in the defect density in the regrown areas.

The continuation of the pendeo-epitaxial growth results in coalescence with adjacent growth fronts and the formation of a continuous layer of GaN, as observed in Fig. 5. This also results in the practical elimination of all dislocations stemming from the heteroepitaxial growth of GaN/AlN on SiC. Clearly visible in Fig. 5(a) are the voids that form when adjacent growth fronts coalesce. Optimization of the pendeo-epitaxial growth technique should eliminate these undesirable defects.

The maximum diameter of commercially available 6H- and 4H-SiC substrates is currently limited to approximately two inches. As such, the development of a process route for achieving the pendeo-epitaxial growth of (0001)GaN on (111)Si was undertaken. Unlike silicon carbide and sapphire substrates, the development of process routes leading to the growth of GaN films on silicon substrates have lagged behind. The slow progress has been

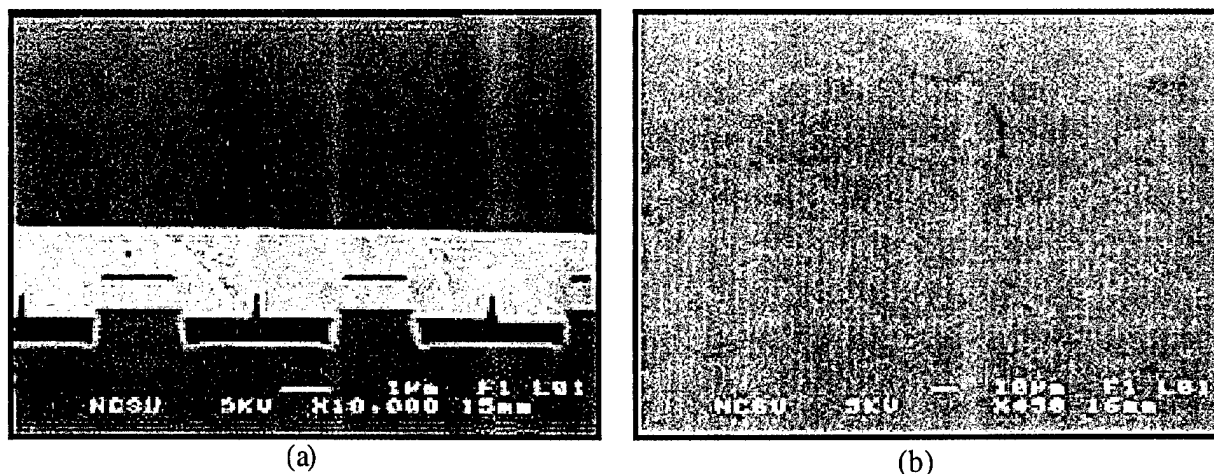


Figure 5. Pendeo-epitaxial growth with coalescence over and between the seed forms resulting in a single GaN layer. 5(a) Cross-section SEM. 5(b) Plane-view SEM.

due in part to the difficulty in the nucleation and two dimensional growth of GaN caused by a combination of significant mismatches in lattice parameters and coefficients of thermal expansion and the chemical stability of the phases in the growth environment. To address these concerns, a 3C-SiC transition layer was employed between the Si wafer and the AlN buffer layer for three reasons. Firstly, an on-axis (111)Si substrate was used which allowed for deposition of the (111)3C-SiC polytype. The SiC layer is preferred for the growth of the 2H-AlN buffer layer of sufficient quality for the subsequent growth of the single crystal GaN seed layer. Secondly, as described above, PE growth of GaN is obtained on SiC because under the growth conditions used for this growth, Ga and N atoms will not bond to the SiC surface in numbers and in time sufficient to cause gallium nitride nuclei to form. Thirdly, the 3C-SiC layer is needed as a diffusion barrier to prevent the interaction of Si atoms with the Ga and N species found in the growth environment. If there is either no diffusion barrier or a diffusion barrier of insufficient thickness, the Si atoms from the substrate have sufficient energy at the temperatures used for PE growth to diffuse to the surface of the AlN buffer layer and react with the gallium nitride layer. This results in the formation of large voids in the underlying Si substrate, the “poisoning” of the GaN film, and the formation of polycrystalline GaN-containing material.

The results of an SEM analysis of PE-grown GaN on a (111)Si substrate is shown in Fig. 6. The rough surface morphologies of the (111)3C-SiC and the AlN buffer layer as well as the relatively poor quality of the GaN seed layer are clearly visible. In contrast, the pendeo-epitaxially grown GaN is of relatively superior quality in terms of surface roughness. Analysis via TEM of the PE GaN layer and optimization of the process routes to improve the PE technique using 3C-SiC are the subjects of ongoing research. Finally, Fig. 7 shows a SEM image of coalesced pendeo-epitaxially grown GaN on a silicon substrate.

D. Conclusions

We have reported on the development of pendeo-epitaxial process routes as a potential way of growing uniformly low-defect density thin films over the entire surface of a substrate.

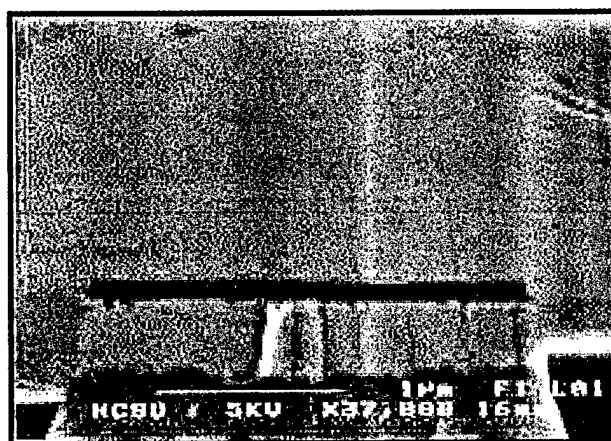


Figure 6. Cross-sectional SEM of pendeo-epitaxial GaN grown on a (111)Si substrate. Clearly visible is the rough surface morphology of the AlN buffer layer and 3C-SiC transition layer.

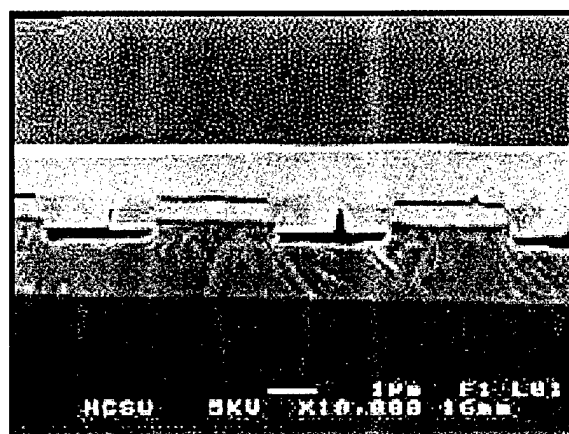


Figure 7. Low magnification cross-sectional SEM of pendeo-epitaxial GaN on a (111)Si substrate and a 3C-SiC transition layer showing coalescence over and between GaN seed forms.

In particular, we have achieved a method to grow GaN using pendeo-epitaxy on 6H-SiC substrates. We have demonstrated both discrete pendeo-epitaxial structures and coalesced layers of GaN. In addition, we report our preliminary results regarding the ability to grow pendeo-epitaxial GaN on silicon substrates. This latest development provides a possible pathway for the fabrication of device quality GaN thin films grown on large area silicon wafers.

E. Acknowledgements

The authors acknowledge Cree Research, Inc. and Motorola for the SiC and the silicon wafers respectively. This work was supported by the Office of Naval Research under

contracts N00014-96-1-0765 and N00014-98-1-0384 (Colin Wood, Technical Monitor) and N00014-98-1-0654 (John Zolper, Technical Monitor).

F. References

1. R. Underwood, D. Kapolnek, B. Keller, S. Keller, S. Denbaars, and U. Mishra, Topical Workshop on Nitrides, Nagoya, Japan, September, 1995.
2. Y. Kato, S. Kitamura, K. Hiramatsu, and N. Sawaki, *J. Cryst. Growth*, **144**, 133 (1994).
3. O. Nam, M. Bremser, B. Ward, R. Nemanich, and R. Davis, *Mat. Res. Soc. Symp. Proc.*, **449**, 107 (1997).
4. O. Nam, M. Bremser, B. Ward, R. Nemanich, and R. Davis, *Jpn. J. Appl. Phys., Part 1* **36**, L532 (1997).
5. A. Sakai, H. Sunakawa, and A. Usui, *Appl. Phys. Lett.*, **73**, 481 (1998).
6. H. Marchand, X. Wu, J. Ibbetson, P. Fini, P. Kozodoy, S. Keller, J. Speck, S. Denbaars, and U. Mishra, *Appl. Phys. Lett.*, **73**, 747 (1998).
7. T. Zheleva, O. Nam, M. Bremser, and R. Davis, *Appl. Phys. Lett.*, **71**, 2472 (1997).
8. O. Nam, T. Zheleva, M. Bremser, and R. Davis, *Appl. Phys. Lett.*, **71**, 2638 (1997).
9. H. Zhong, M. Johnson, T. McNulty, J. Brown, J. Cook Jr., J. Schetzina, *Materials Internet Journal, Nitride Semiconductor Research*, **3**, 6, (1998).
10. S. Nakamura, M. Senoh, S. Nagahama, N. Iwasa, T. Yamada, T. Matsushita, H. Kiyoku, Y. Sugimoto, T. Kozaki, H. Umemoto, M. Sano, and K. Chocho, *Proc. of the 2nd Int. Conf. On Nitride Semicond.*, Tokushima, Japan, October, 1997.
11. T. Zheleva, S. Smith, D. Thomson, K. Linthicum, T. Gehrke, P. Rajagopal, R. Davis, (submitted to the *Journal of Electronic Materials*).
12. K. Linthicum, T. Gehrke, D. Thomson, E. Carlson, P. Rajagopal, T. Smith, R. Davis, (submitted to *Applied Physics Letters*).
13. T. Weeks, M. Bremser, K. Ailey, E. Carlson, W. Perry, and R. Davis, *Appl. Phys. Lett.*, **67**, 401 (1995).
14. C. Zorman, A. Fleischman, A. Dewa, M. Mehregany, C. Jacob, S. Nishino, and P. Pirouz, *J. Appl. Phys.*, **78**, 5136 (1995).
15. T. Gehrke, K. Linthicum, D. Thomson, P. Rajagopal, A. Batchelor, R. Davis, *Mat. Res. Soc. Symp.*, this volume.
16. D. Thomson, T. Gehrke, K. Linthicum, P. Rajagopal, T. Zheleva, R. Davis, *Mat. Res. Soc. Symp.*, this volume.
17. T. Zheleva, et al., *Mat. Res. Soc. Symp.*, this volume.

Distribution List

Dr. Colin E. Wood Office of Naval Research Electronics Division, Code: 312 Ballston Tower One 800 N. Quincy Street Arlington, VA 22217-5660	3
Administrative Grants Officer Office of Naval Research Regional Office Atlanta 100 Alabama Street, NW, Suite 4R15 Atlanta, GA 30303-3104	1
Director, Naval Research Laboratory ATTN: Code 5227 4555 Overlook Drive Washington, DC 20375-5326	1
Defense Technical Information Center 8725 John J. Kingman Road, Suite 0944 Ft. Belvoir, VA 22060-6218	2